



Emissions Report: Ultrafine particles (UFPs) and volatile organic compounds (VOCs) from desktop 3D printers

Filament: PolyLite PLA Black

Printer: LulzBot Mini

Authors: Parham Azimi, Ph.D., Brent Stephens, Ph.D., Department of Civil, Architectural, and Environmental Engineering, Built Environment Research Group (<http://built-envi.com>), Illinois Institute of Technology

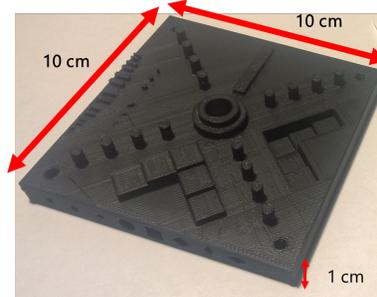


Figure 1. Printed standardized test part from NIST used for emissions testing

Summary:

The goal of this work is to experimentally characterize the emissions of ultrafine particles (UFPs, or particles <100 nm) and speciated volatile organic compounds (VOCs) when printing a standardized test part with a desktop 3D printer and polymer filament following manufacturer recommended settings.

Methods:

We conducted controlled environmental chamber testing following methods described in Azimi et al. (2016) *Environ Sci Technol* 50(3):1260-1268. All measurements were conducted inside a well-mixed 3.6 m³ stainless steel chamber. The 3D printer bed was prepared for printing before sealing the chamber by applying small amounts of adhesive from glue sticks following manufacturer recommendations. We printed a $10 \times 10 \times 1$ cm standardized sample from the National Institute of Standards and Technology (NIST), as shown in Figure 1.

Results:

UFP emissions

Figure 2a shows time-varying total UFP concentrations resulting from the single print test and Figure 2b shows estimates of time-varying total UFP emission rates. The left guideline in Figure 2a shows the moment that the printer began warming up prior to printing, which we considered part of the printing emissions period. The second guideline shows the moment that the printer stopped printing. The data was smoothed using MATLAB[®] 2015 and the corresponding coefficient of determination ($SM-R^2$) is shown in Figure 2a. The error bars in Figure 2b show an estimated $\sim 45\%$ uncertainty in the UFP emission rate estimates. The solid line and the upper and lower dashed lines in Figure 2b demonstrate the median and interquartile range of the estimated UFP emission rates. The number of negative estimated emissions (NNEE) is also provided in Figure 2b.

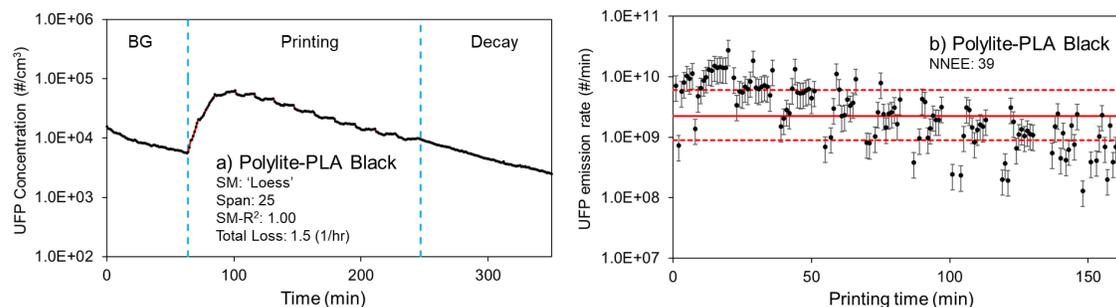


Figure 2. a) Time-varying UFP concentrations inside the chamber during background, printing, and decay time periods, and b) estimates of time-varying UFP emission rates during the printing period

Table 1 summarizes the estimated UFP emission rate results. The UFP concentration in the chamber increased for about 20 minutes once the printing period began and then decayed back towards the background level throughout the rest of the printing period. The median UFP emission rate was about an order of magnitude lower than the average UFP emission rate of 15 printer and filament combinations reported in Azimi et al. 2016 (e.g., a median UFP emission rate of $\sim 2.3 \times 10^9$ #/min compared to an average of $\sim 2 \times 10^{10}$ #/min from the 15 printer and filament combinations).

Table 1. Summary of total UFP emission rate results

Average (\pm SD) (#/min)	Median (#/min)	Max (#/min)	Min (#/min)	Total UFPs emitted (#)	Emission per mass of filament (#/g)	Printing duration (mins)	Printing temperature ($^{\circ}$ C)	
							Nozzle	Bed
4.0×10^9 ($\pm 4.5 \times 10^9$)	2.3×10^9	2.8×10^{10}	7.9×10^7	7.1×10^{11}	1.3×10^{10}	184	205	60

Speciated VOC emission rates

Table 2 summarizes estimates of individual speciated VOC and Σ VOC emission rates (i.e., the sum of the emission rates of the top 5 speciated VOCs with the highest individual emission rates) from the tested filament. "Lactide", "Acetic Acid", and "2-Butenoic acid, methyl ester, (Z)-" had the highest individual VOC emission rates from the tested filament. Σ VOC emissions from this filament and printer combination (~ 9.89 μ g/min) were low relative to an average of ~ 67 μ g/min from 15 printer and filament combinations reported in Azimi et al. (2016). The uncertainty in individual VOC emission rates is estimated to be $\sim 36\%$. It is also noticeable that both estimated VOC and UFP emission rates from the PolyLite PLA filament with black color was higher than the same filament with white color.

Table 2. Summary of top-five individual speciated VOC emission rates

Compound	Lactide	Acetic acid	2-Butenoic acid, methyl ester, (Z)-	1,6-Dideoxy-l-mannitol	Ethylamine	Σ VOC
E (μ g/min)	4.15	1.96	1.84	1.02	0.91	9.89